

118
6-2-77

ORNL/TM-5783

Dr 1071

Compatibility Studies of Potential Molten-Salt Breeder Reactor Materials in Molten Fluoride Salts

J. R. Keiser

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

OAK RIDGE NATIONAL LABORATORY

OPERATED BY UNION CARBIDE CORPORATION FOR THE ENERGY RESEARCH AND DEVELOPMENT ADMINISTRATION

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency Thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

DISCLAIMER

Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.

Printed in the United States of America. Available from
National Technical Information Service
U.S. Department of Commerce
5285 Port Royal Road, Springfield, Virginia 22161
Price: Printed Copy \$4.00; Microfiche \$3.00

This report was prepared as an account of work sponsored by the United States Government. Neither the United States nor the Energy Research and Development Administration/United States Nuclear Regulatory Commission, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness or usefulness of any information, apparatus, product or process disclosed, or represents that its use would not infringe privately owned rights.

ORNL/TM-5783
Distribution
Category UC-76

Contract No. W-7405-eng-26

METALS AND CERAMICS DIVISION

COMPATIBILITY STUDIES OF POTENTIAL MOLTEN-SALT BREEDER
REACTOR MATERIALS IN MOLTEN FLUORIDE SALTS

J. R. Keiser

Date Published: May 1977

NOTICE
This report was prepared as an account of work sponsored by the United States Government. Neither the United States nor the United States Energy Research and Development Administration, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness or usefulness of any information, apparatus, product or process disclosed, or represents that its use would not infringe privately owned rights.

NOTICE This document contains information of a preliminary nature. It is subject to revision or correction and therefore does not represent a final report.

OAK RIDGE NATIONAL LABORATORY
Oak Ridge, Tennessee 37830
operated by
UNION CARBIDE CORPORATION
for the
ENERGY RESEARCH AND DEVELOPMENT ADMINISTRATION

MASTER

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

THIS PAGE
WAS INTENTIONALLY
LEFT BLANK

CONTENTS

	Page
ABSTRACT	1
INTRODUCTION	1
EXPERIMENTAL METHODS	3
EXPERIMENTAL RESULTS	7
Thermal-Convection Loop 21A	7
Thermal-Convection Loop 23	10
Thermal-Convection Loop 31	15
Thermal-Convection Loops 18C and 24	17
Forced-Circulation Loop FCL-2B	17
CONCLUSIONS	21
ACKNOWLEDGMENTS	21

COMPATIBILITY STUDIES OF POTENTIAL MOLTEN-SALT BREEDER
REACTOR MATERIALS IN MOLTEN FLUORIDE SALTS

J. R. Keiser

ABSTRACT

This report summarizes the molten fluoride salt compatibility studies carried out during the period 1974-76 in support of the Molten-Salt Reactor Program. Thermal-convection and forced-circulation loops were used to measure the corrosion rate of selected alloys. Results confirmed the relationship of time, initial chromium concentration, and mass loss developed by previous workers. The corrosion rates of Hastelloy N and Hastelloy N modified by the addition of 1-3 wt % Nb were well within the acceptable range for use in an MSBR.

INTRODUCTION

The purpose of this report is to summarize the corrosion studies carried out for the Molten-Salt Reactor Program during the period September 1974 through May 1976. These studies were intended to determine the corrosion resistance of potential Molten-Salt Breeder Reactor containment vessel materials in molten fluoride salt. The nickel-base alloy Hastelloy N was used successfully for the containment vessel of an experimental molten-salt reactor, the Molten-Salt Reactor Experiment. However, the discovery of irradiation embrittlement and grain boundary embrittlement by the fission product tellurium led to a program to develop an alloy that would be sufficiently resistant to the conditions. To ensure that any new or modified alloy would have a high resistance to corrosion by the fluoride salt, salt-metal corrosion studies were made. Materials investigated include Hastelloy N, chromium and niobium modifications of Hastelloy N, Inconel 601, and type 316 stainless steel. The stainless steel was tested in LiF-BeF₂ (65-35 mole %), and the other alloys were tested in MSBR fuel salt, LiF-BeF₂-ThF₄-UF₄ (72-16-11.7-0.3 mole %).

Previous reserachers^{1,2} have measured the corrosion resistance of Hastelloy N and two types of stainless steel in various fluoride salt mixtures. Their work has shown a multicomponent alloy is corroded by the oxidation and removal of the least noble component. For Hastelloy N, the least noble component is chromium. Fluoride salts can oxidize chromium by reaction with impurities in the salt such as HF, NiF₂, and FeF₂ and by reaction with constituents of the salt. Impurity reactions expected are



and



The salt constituent UF₄ can give the reaction:



If salt containing UF₄ and a small amount of impurities is put into a Hastelloy N system in which the salt circulates nonisothermally, chromium will initially be removed from all parts of the system because of reaction with both impurities and UF₄. The impurity reactions are expected to go to completion fairly rapidly so that they will have an effect only on the short-time corrosion results. On the other hand, since the equilibrium constant for reaction (3) is a function of temperature, this reaction provides a means for the continuous transfer of

¹J. W. Koger, *Alloy compatibility with LiF-BeF₂ Salts Containing ThF₄ and UF₄*, ORNL/TM-4286 (December 1972).

²J. H. DeVan, *Effect of Alloying Additions on Corrosion Behavior of Nickel-Molybdenum Alloys in Fused Fluoride Mixtures* M.S. Thesis, University of Tennessee, August 1960.

chromium from the hotter sections of the system to the cooler sections. The amount of chromium, ΔM , removed from a unit area of surface can be shown to be:

$$\Delta M = BC_0 \sqrt{Dt} \quad (4)$$

where B is a temperature-dependent constant, C_0 is the initial concentration of chromium in the alloy, and D is the diffusivity of chromium in the alloy. The limiting step for this mass transfer has been shown to be the diffusion of chromium in the metal when Hastelloy N is the alloy considered. If other strong fluoride formers — such as Ti, Nb, or Al — are present in the alloy, mass transfer of these elements would be expected to occur by the same mechanism as discussed above.

EXPERIMENTAL METHODS

Our corrosion studies have been carried out in five thermal-convection loops and one forced-circulation loop. Figures 1 and 2 show schematic drawings of these loops. These loops circulate salt around a system across which a temperature gradient is maintained. For most of these loops the temperature limits were maintained at 704 and 566°C (1300 and 1050°F), the proposed maximum and minimum temperatures for the fuel salt of an MSBR. Other important features of these loops are the removable corrosion specimens and the accesses to the salt to permit insertion of electrodes for controlled-potential voltammetry. Voltammetric measurements, which were made by members of the Analytical Chemistry Division, allowed us to make on-line determinations of the oxidation potential and corrosion product concentration of the salt. Detailed explanations of voltammetry are available elsewhere.^{3,4} The operating conditions for each of the loops are described in Table 1.

³M. W. Rosenthal, P. N. Haubenreich, P. B. Briggs, Comps., *The Development Status of Molten Salt Breeder Reactors.*, ORNL-4812 (August 1972) pp. 153-57.

⁴J. R. Keiser, J. H. DeVan, and D. L. Manning, *The Corrosion Resistance of Type 316 Stainless Steel to Li₂BeF₄*, ORNL/TM-5782 (April 1977).

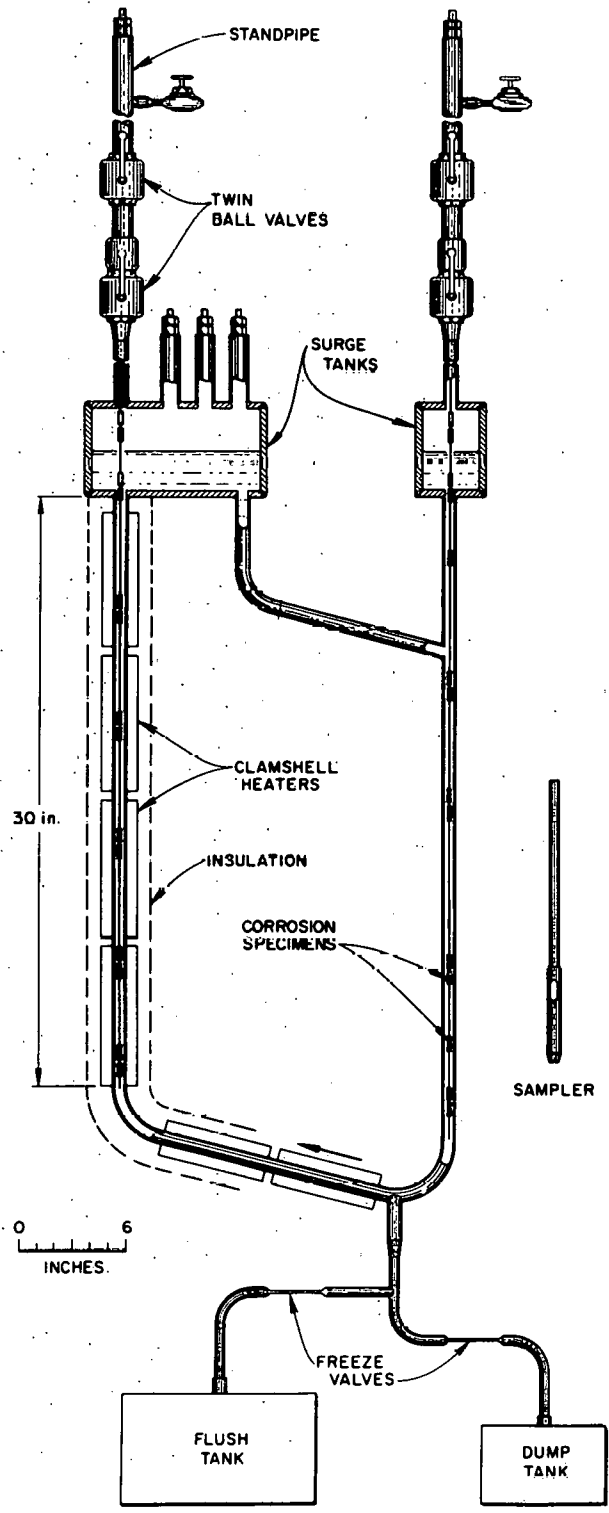


Fig. 1. Schematic of Thermal-Convection Loop. Scale is 0.15 m. Height shown is 0.76 m.

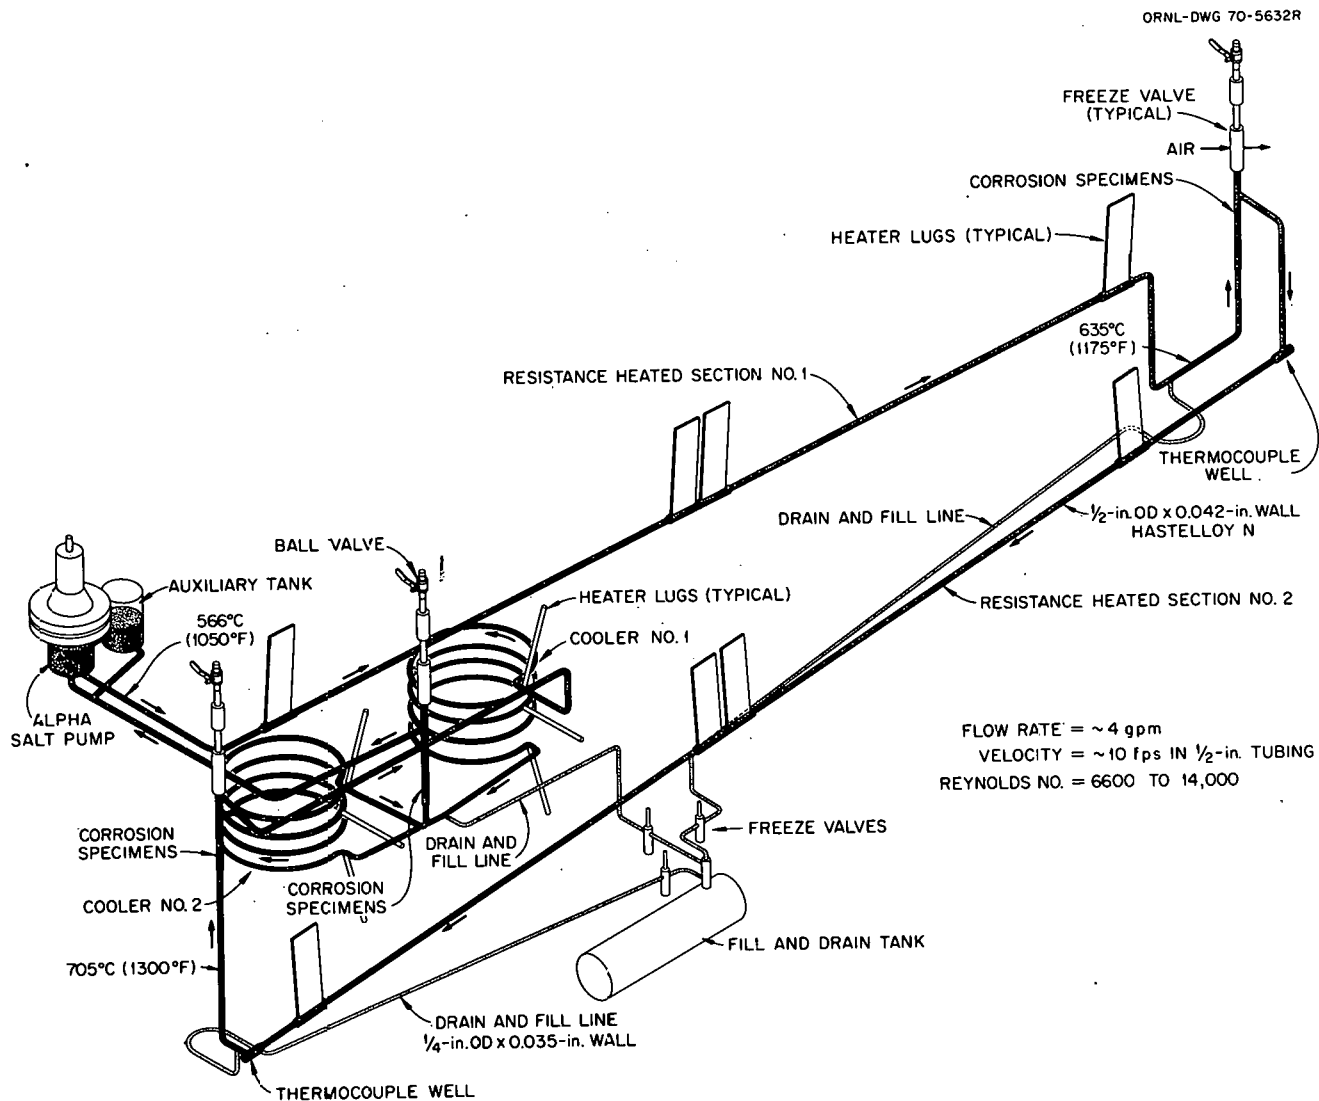


Fig. 2. Schematic of Molten-Salt Forced-Convection Corrosion Loop MSR-FCL-2 b. Flow rate \approx 0.25 liter/sec; velocity \approx 3 m/sec in 13-mm tubing; loop tubing is 13-mm OD by 1.07-mm wall; drain and fill line is 6.4-mm OD by 0.9-mm wall.

Table 1. Loop Operating Conditions

Loop	Loop Material	Specimen Material	Salt	Operating Temperature, °C		Purpose
				Max	Min	
<u>Thermal-Convection Loops</u>						
21A	Hastelloy N	Hastelloy N, 1%-Nb-mod Hastelloy N	MSBR Fuel	704	566	1. Analytic method development 2. Base-line corrosion data
23	Inconel 601	Inconel 601	MSBR Fuel	704	566	1. Measure corrosion rate of high-Cr alloy (Inconel 601)
		Graphite	MSBR Fuel	677	550	2. Investigate Graphite UF ₃ Reaction
31	Type 316 Stainless Steel	Type 316 Stainless Steel	Li ₂ BeF ₄	649	493	1. Measure corrosion rate of type 316 stainless steel in potential coolant salt 2. Investigate effect of Be addition to salt
24	Hastelloy N	7%-Cr-mod Hastelloy N, 12%-Cr-mod Hastelloy N, 3.4%-Nb-mod Hastelloy N	MSBR Fuel	704	566	1. Measure corrosion rate of modified Hastelloy N alloys
18C	Hastelloy N	10%-Cr-mod Hastelloy N, 15%-Cr-mod Hastelloy N	MSBR Fuel	704	566	1. Measure corrosion rate of modified Hastelloy N alloys
<u>Forced-Circulation Loop</u>						
FCL-2B	Hastelloy N	Hastelloy N, 1%-Nb-mod Hastelloy N	MSBR Fuel	704	566	1. Base-line corrosion data in high-velocity salt

EXPERIMENTAL RESULTS

Thermal-Convection Loop 21A

Hastelloy N loop NCL 21A was the first loop to be put into operation when the Molten-Salt Reactor Program was resumed in 1974. As such, the loop was used to obtain base-line corrosion data for Hastelloy N and to provide a test bed for voltammetry measurements of MSBR fuel salt. The voltammetry results showed that the oxidation potential as reflected by the U(IV)/U(III) ratio remained quite high throughout the 17.5 months of operation. In fact, with a U(IV)/U(III) ratio of about 10^4 loop 21A contained the most oxidizing salt of all the loop experiments.

The first specimens used in this loop were made of Hastelloy N and were removed for examination about every 2500 hr. Figure 3 shows the weight change as a function of the exposure time for these specimens for up to 10,000 hr in salt. From this figure the rate of the weight change clearly decreased with time. Figure 4 shows that the change in weight varies as the square root of time, as predicted from Eq. (4).

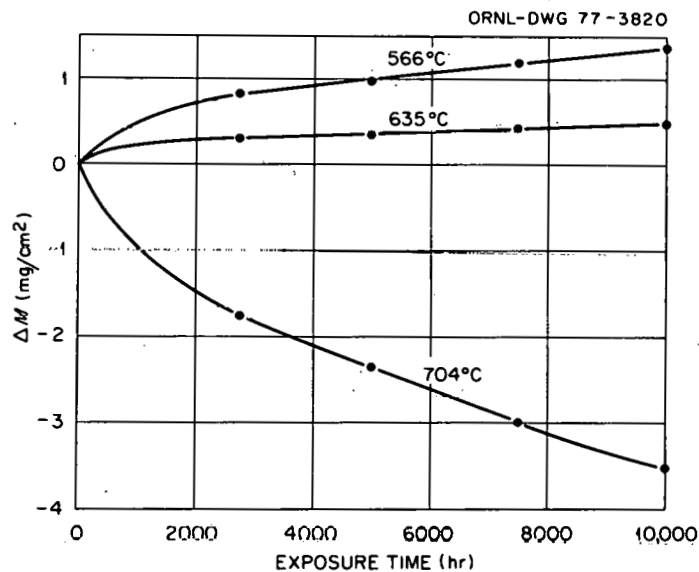


Fig. 3. Weight Change vs Exposure Time for Hastelloy N Specimens Exposed to MSBR Fuel Salt at 566, 635, and 704°C in Thermal-Convection Loop 21A.

ORNL-DWG 76-4843

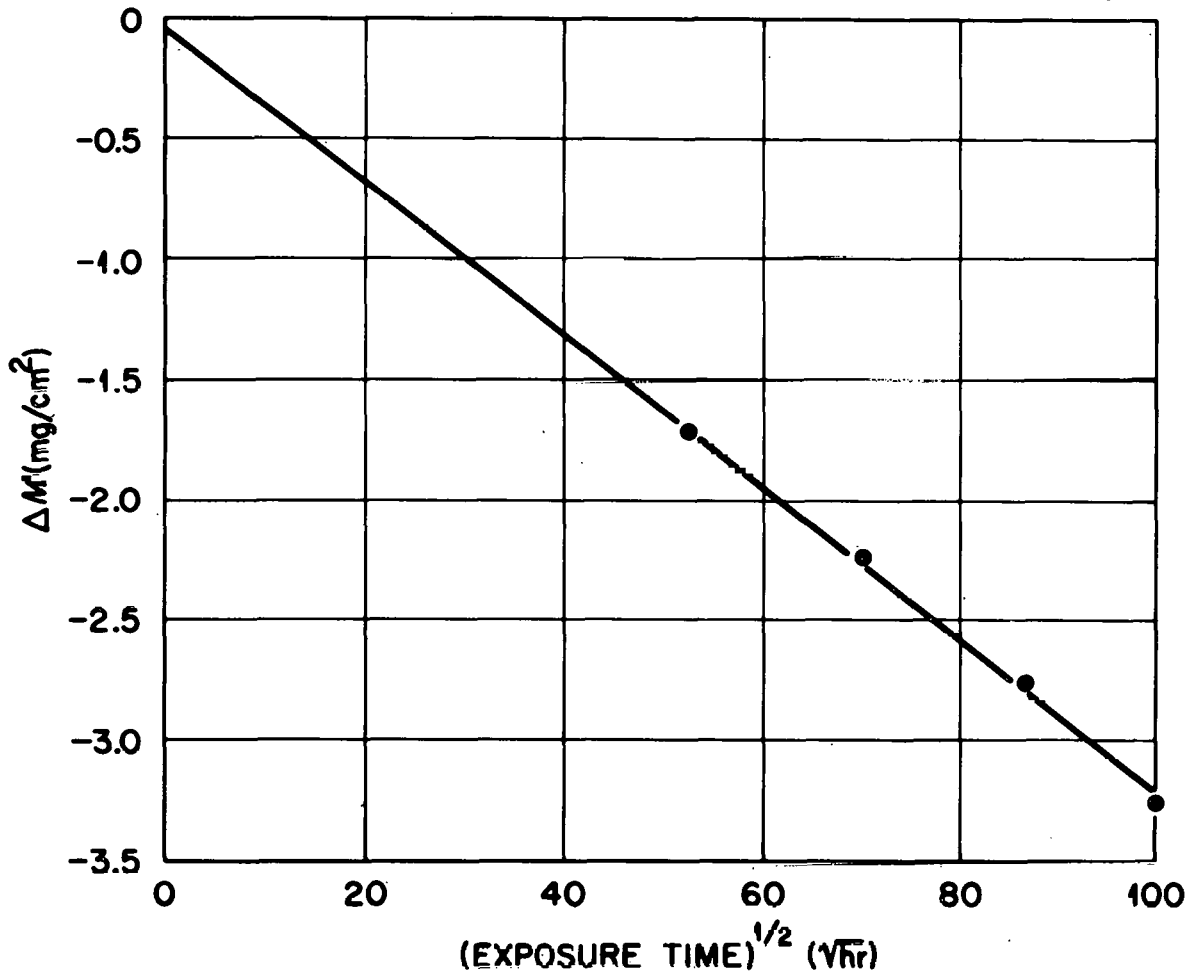


Fig. 4. Weight Change vs Square Root of Exposure Time for Hastelloy N Specimen Exposed to MSBR Fuel Salt at 690°C in Thermal-Convection Loop 21A.

Specimens that had been exposed for 7500 hr in the hottest and coldest parts of the loop were examined metallographically. As is evident in Fig. 5 the pitting on the higher temperature specimen was limited to about 5 μm , indicating that the effect of the salt was relatively mild.

Following the 10,000-hr exposure of standard Hastelloy N, loop 21A was used to test specimens of 1%-Nb-modified Hastelloy N (experimental heat 522). Only a short exposure was achieved with these specimens before a power supply malfunction terminated the experiment, but the short-time corrosion results (Table 2) compare very favorably with results for standard Hastelloy N.

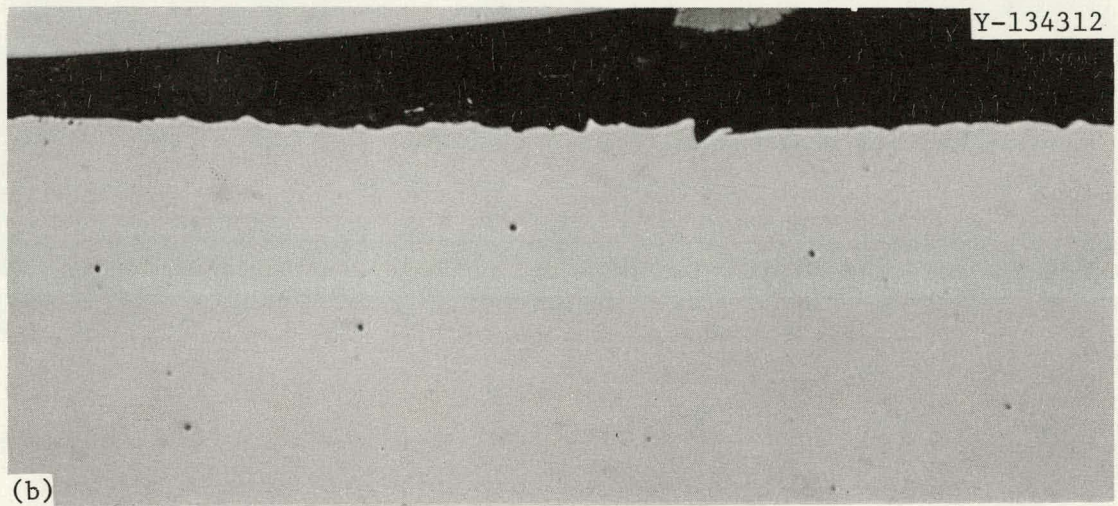
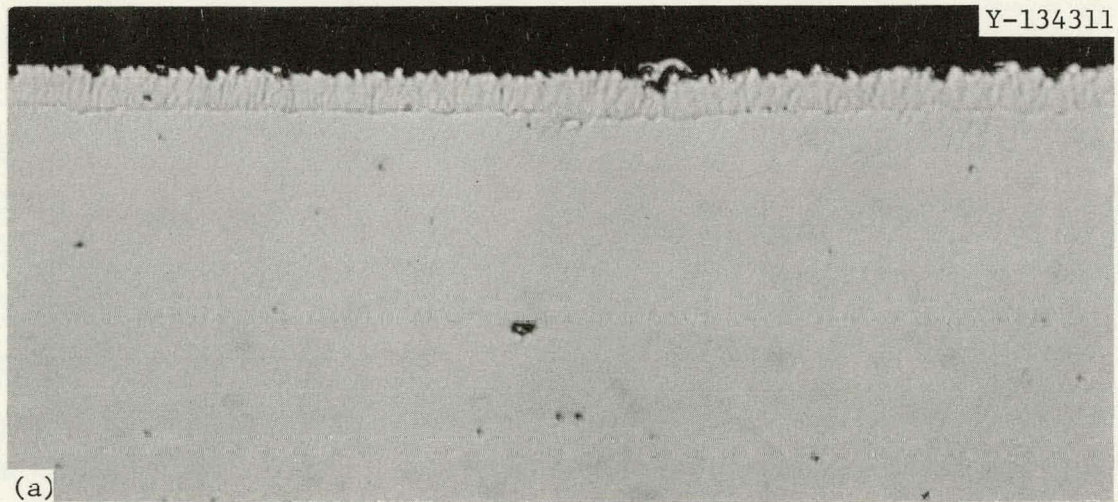


Fig. 5. Hastelloy N Exposed to MSBR Fuel Salt for 7500 hr at (a) 704 and (b) 566°C. 500×.

Table 2. Hastelloy N Corrosion Rate Measurements from Loop 21A

Alloy	Total Exposure (hr)	Corrosion Rate, $\text{mg cm}^{-2} \text{ year}^{-1}$, at Each Exposure Temperature		
		566°C	635°C	704°C
Standard	10,009	+1.17	+0.39	-3.09
1% Nb Modified	1,004	0.0	-0.25	-3.30

Thermal-Convection Loop 23

The observation that the high-chromium alloy Inconel 601 (23 wt % Cr) resisted intergranular attack by tellurium led to the construction of a thermal-convection loop to determine how severe the corrosion by MSBR fuel salt would be. After the new loop was filled with salt, voltammetric techniques were used to follow the change in the U(IV)/U(III) ratio as an indication of the extent of the initial reaction between chromium and UF_4 . The U(IV)/U(III) ratio decreased very rapidly, dropping to about 40 within a few days, meaning that considerable reaction was probably occurring between the salt and this Inconel 601 loop. Inconel 601 specimens exposed 721 hr all showed a weight loss, and that shown by the hottest specimen was very large ($>30 \text{ mg cm}^{-2} \text{ year}^{-1}$). Furthermore, the material lost by the hottest specimens was not removed uniformly from the surface, but resulted in the formation of the porous surface structure shown in Fig. 6. As shown in Fig. 7, electron microprobe examination of this specimen showed high thorium concentration in the pores. Since the only known source of thorium was the ThF_4 contained in the salt, the salt likely penetrated the pores. Continuous line scans made with the microprobe for the elements Ni, Cr, and Th, shown in Fig. 8, clearly show the depletion of chromium near the surface. These results provide further evidence of the presence of thorium in the pores. Diffusion calculations provide another piece of evidence indicating that salt must have penetrated the pores. Based on the bulk chromium concentration of 23 wt %, microprobe measurements⁵ determined a chromium concentration of 6.6 wt % at the surface of the specimen in Fig. 6. From these concentrations, a depletion depth of 80 μm taken from Fig. 8, and diffusion values taken from Evans, Koger, and DeVan,⁶ we calculate that the exposure time would have to be nearly 1000 times greater to attain this concentration profile as a result of bulk diffusion alone at 704°C. To obtain this

⁵R. S. Crouse, ORNL, Private Communication, July 1975.

⁶R. B. Evans III, J. W. Koger, and J. H. DeVan, *Corrosion in Polythermal Loop Systems II. A Solid State Diffusion Mechanism With and Without Liquid Film Effects*, ORNL-4575, Vol. 2 (June 1971).

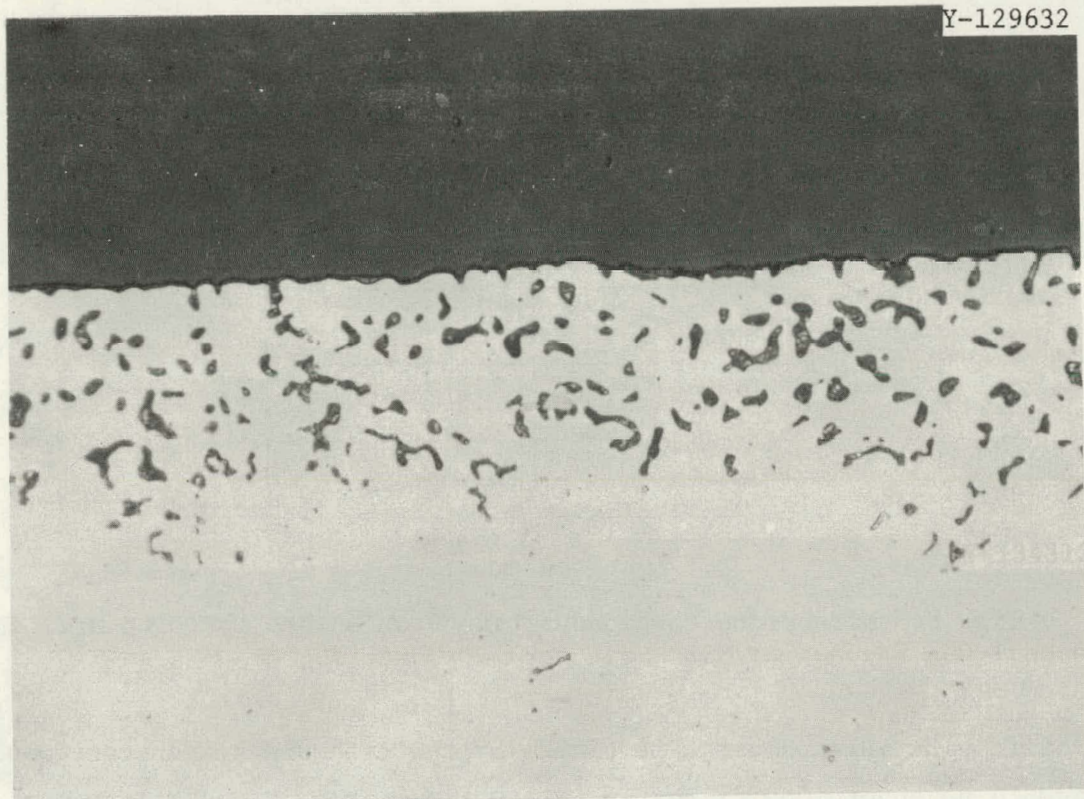


Fig. 6. Inconel 601 Exposed to MSBR Fuel Salt for 721 hr at 704°C. 500 \times .

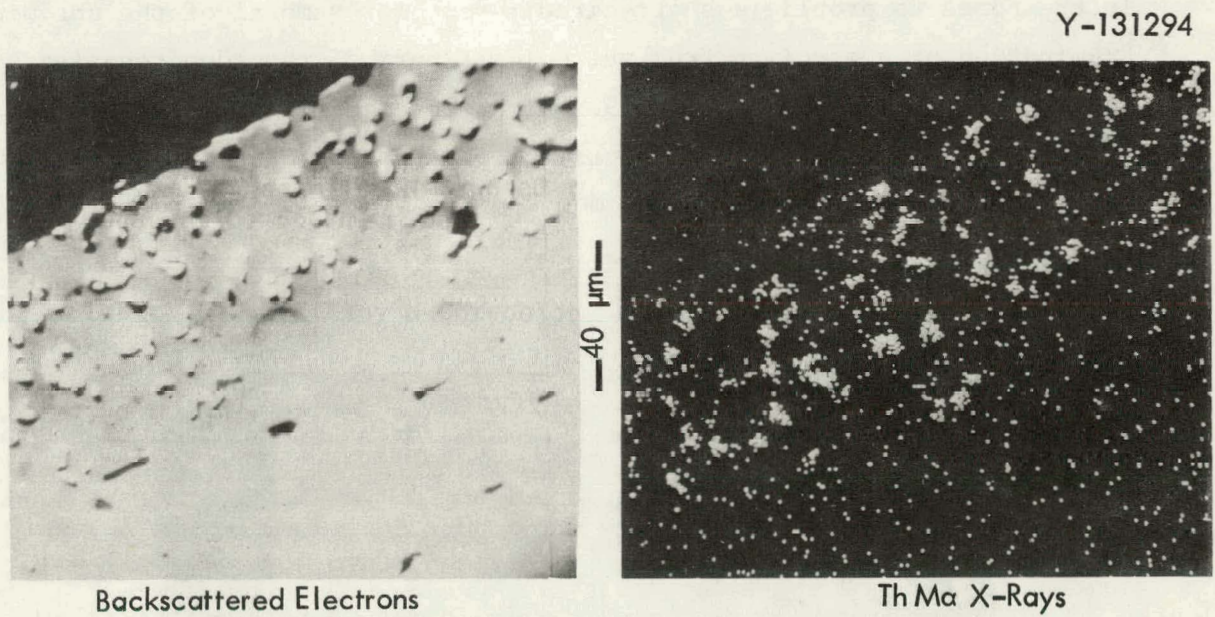


Fig. 7. Electron-Beam Scanning Images of Inconel 601 Exposed to MSBR Salts for 720 hr at 704°C.

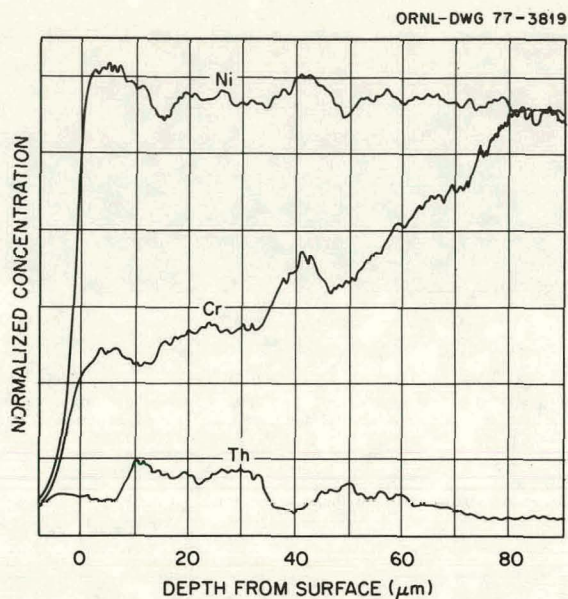


Fig. 8. Microprobe Continuous Line Scan Across Corroded Area in Inconel 601 Exposed to MSBR Salt for 720 hr at 704°C.

profile with an exposure time of 721 hr the exposure temperature would have to be about 1000°C, nearly 300°C higher than it was. Thus, to establish the gradient that was observed, salt was most likely present in the pores to provide a short-circuit path for removal of the chromium. Examination of a specimen from the coldest part of the loop revealed surface deposits, shown in Fig. 9, which were identified by microprobe analysis as chromium. The conclusion from this test is that Inconel 601 would be unsuitable for use in a molten-salt breeder reactor.

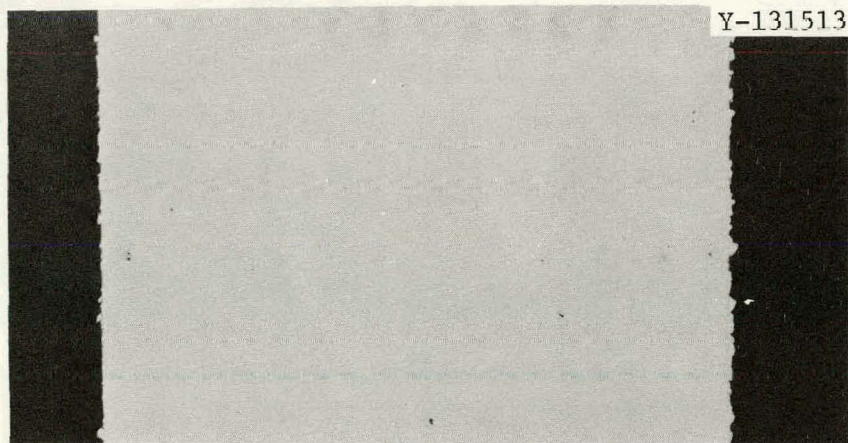


Fig. 9. Inconel 601 Exposed to MSBR Fuel Salt for 721 hr at 570°C. 500×.

It is expected that the lower limit for the U(IV)/U(III) ratio in an MSBR will be determined by the conditions under which the reaction



proceeds to the right. Because the U(IV)/U(III) ratio of the salt in loop 23 had decreased to less than 6, we decided to try to reproduce the results of Toth and Gilpatrick,⁷ shown in Fig. 10, which predict that UC₂ should be stable at the lowest temperatures that could be maintained in this loop, 545–550°C. However, graphite specimens exposed to the salt for 530 hr did not show any evidence of UC₂. Since the specimens used were made of pyrolytic graphite, the high density of the material likely limited contact of the salt and graphite. The experiment was repeated by exposing a less dense graphite for 530 hr,

⁷L. M. Toth and L. O. Gilpatrick, *The Equilibrium of Dilute UF₃ Solutions Contained in Graphite*, ORNL/TM-4056 (December 1972).

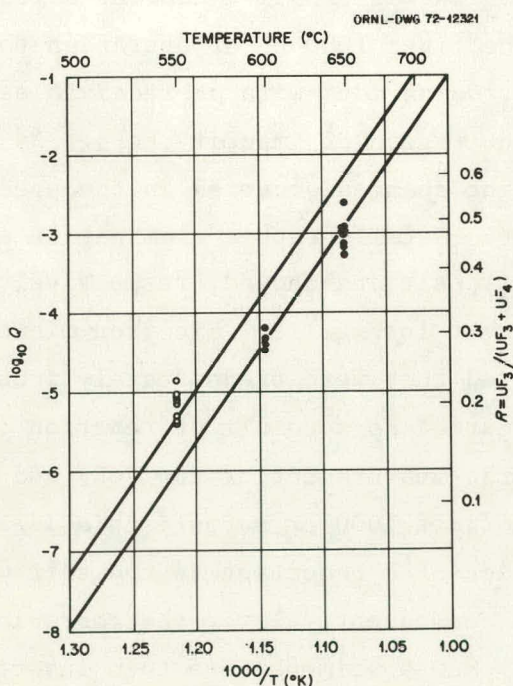


Fig. 10. Equilibrium Quotients, $Q = (\text{UF}_3)^4 / (\text{UF}_4)^3$, Versus Temperature for $\text{UC}_2 + 3\text{UF}_4(\text{d}) \rightleftharpoons 4\text{UF}_3(\text{d}) + 2\text{C}$ in the Solvent LiF-BeF₂-ThF₄ (72-16-12 mole %).

then checking the graphite surface for the presence of a new phase by x-ray diffraction. A new phase was found, and it was tentatively identified by O. B. Cavin as UO_2 . If indeed this compound was UO_2 , it probably resulted from a uranium fluoride-water reaction, but it could have come from the hydrolysis of UC_2 that had been formed by reaction (5). On the basis of information from L. M. Toth⁸ that nucleation of UC_2 under our operating conditions could be very slow, a longer exposure was undertaken. Two specimens of the less dense graphite were exposed for about 3000 hr at a minimum temperature of $555^\circ C$ in salt in which the U(IV)/U(III) ratio had dropped to about 4. However, x-ray analysis of these specimens showed no evidence of a phase other than the salt and graphite. No further investigations were carried out because of the termination of the program.

Thermal-Convection Loop 31

Thermal-convection loop 31 is constructed of type 316 stainless steel, has type 316 stainless steel specimens, and has been used for corrosion measurements with one of the alternative coolant salts, $LiF-BeF_2$ (66-34 mole %). For the first 1000 hr of operation this loop was used to gather base-line corrosion data with as-received salt, which contained a relatively high concentration of impurity FeF_2 . As shown in Fig. 11, fairly significant weight changes occurred in the specimens, especially during the first 500 hr. Metallographic examination of specimens from the hottest and coldest positions showed, respectively, pitting and deposition, as is apparent in Fig. 12. Electron microprobe examination of the deposits indicated they were predominately iron, and we expect that the deposition occurred as a result of reaction (2). Bulk salt analyses and voltammetric measurement of the FeF_2 and CrF_2 concentrations of the salt during the first 1000 hr support this idea.

To learn if addition of a reductant to the salt would decrease the impurity level and consequently lower the corrosion rate, beryllium was added to the salt. New specimens were then inserted, and the corrosion rate was measured for stainless steel in this "reducing" salt. As long

⁸L. M. Toth, private communication.

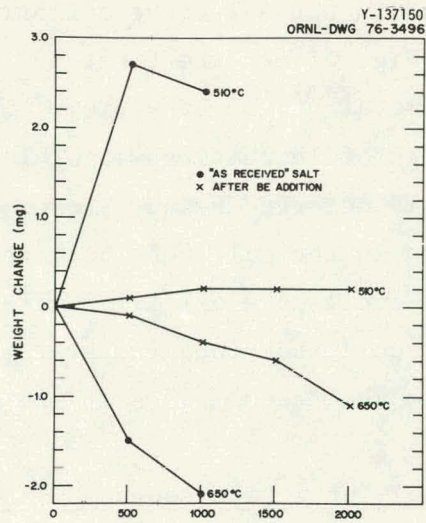


Fig. 11. Weight Change vs Exposure Time for Type 316 Stainless Steel Exposed to LiF-BeF_2 .

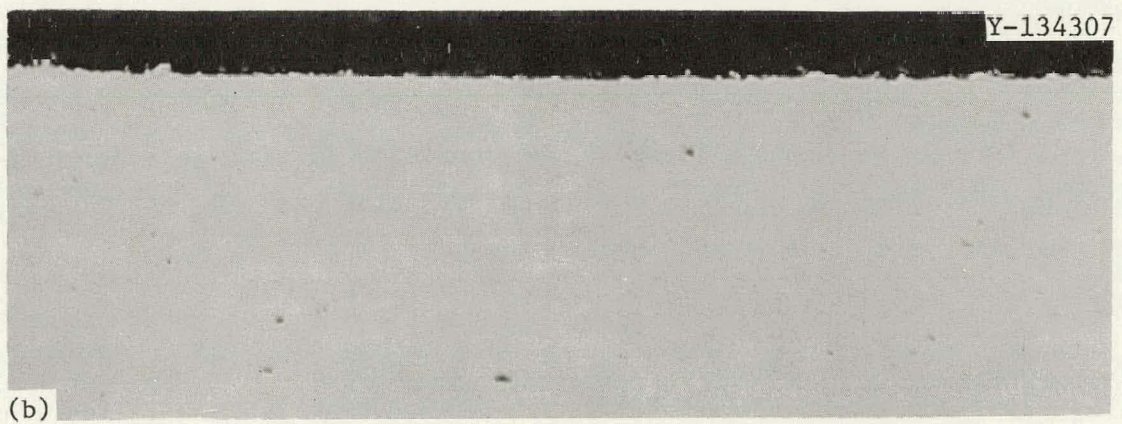


Fig. 12. Type 316 Stainless Steel Exposed to LiF-BeF_2 for 1000 hr at (a) 650 and (b) 510°C. 500 \times .

as the beryllium rod was in the salt, the corrosion rate was extremely low. This is shown in Fig. 11 for the first 500 hr after the addition of beryllium. After removal of the beryllium, the specimen in the hottest position showed a pattern of increasing weight loss as a function of time. This most probably occurred because, once the source of beryllium was removed, the species in the salt were no longer in equilibrium and the salt became progressively more oxidizing with increasing time, especially as moisture would leak into the system. Weight change results for specimens exposed to the "reducing" salt are also shown in Fig. 11.

Thermal-Convection Loops 18C and 24

Hastelloy N loops 18C and 24 were used to determine the effect of chromium concentration on the corrosion rate of Hastelloy N. Alloys such as stainless steels and Inconels with a relatively high chromium content had shown a resistance to grain boundary attack by tellurium that seemed to be roughly proportional to chromium composition. However, increasing the chromium content is, according to Eq. (4), expected to increase the corrosion that will occur because of mass transfer. From these tests and tellurium exposure tests we hoped to learn if there is an optimum chromium concentration. Specimens were fabricated from modified Hastelloy N alloys containing 7, 10, and 12% Cr. Each set of specimens was exposed in one of the loops for a total of 1000 hr, with weight change measured after 500 and 1000 hr. Within experimental error the weight change results (Fig. 13) show the dependence on initial chromium concentration that would be expected according to Eq. (4).

Following completion of the studies with the chromium-modified alloys, loop 24 was used to measure the corrosion rate of 3.4%-Nb-modified Hastelloy N. Results indicate a maximum corrosion rate of less than $2.20 \text{ mg cm}^{-2} \text{ year}^{-1}$ for a 1500-hr exposure.

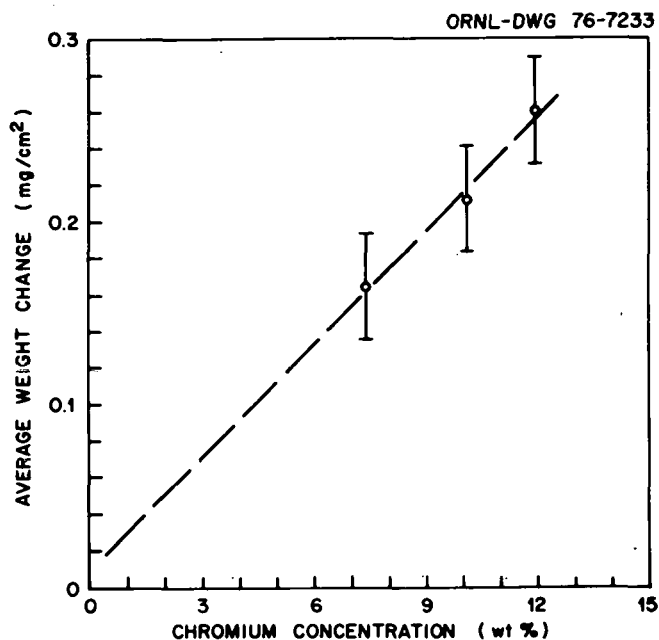


Fig. 13. Effect of Chromium Concentration in Modified Hastelloy N on Weight Change After 1000 hr in MSBR Fuel Salt.

Forced-Circulation Loop FCL-2B

Forced-circulation loop FCL-2B was used initially for fuel salt chemistry investigations. The first fuel salt corrosion investigations were made with standard Hastelloy N in salt with a U(IV)/U(III) ratio of about 100. Thus, the most significant differences between this loop and thermal-convection loop 21A were the oxidation potential of the salt [$\sim 10^2$ vs $\sim 10^4$ in terms of U(IV)/U(III) ratio] and the velocity of the salt 2.5–5 m/sec vs 1 m/min. If Eq. (4) and the ideas that led to its development are correct, we would expect that (1) the only effect of the low U(IV)/U(III) ratio in FCL-2B would probably be a reduction in the initial corrosion compared with NCL 21A, and (2) the high salt velocity would have no effect on mass transfer of chromium since the limiting factor is the diffusion of chromium to the surface of the alloy, not transfer of the chromium from the hot to the cold parts of the system. The results of this study, shown in Table 3, indicate a very low corrosion rate for the 4000-hr exposure. This test was interrupted several times for repairs on the loop and for heat transfer measurements, but that did not seem to have a detrimental effect on the results.

A 4000-hr corrosion test of Hastelloy N in fuel salt with a U(IV)/U(III) ratio of 1000 was planned. Because of the decision to terminate the Molten-Salt Reactor Program, we decided the remaining operating time for this loop could be best spent measuring the corrosion rate of 1%-Nb-modified Hastelloy N, an alloy that had shown good resistance to tellurium attack. Accordingly, a set of such specimens was prepared and inserted into the loop. Because of loop operating difficulties some of the weight changes measured after 500 and 1000 hr were of questionable value. Measurements made after 1500- and 2200-hr exposure were of good quality and are summarized in Table 3 along with some of the 500- and 1000-hr results. Included in this table for comparison are the results for the standard Hastelloy N specimens exposed for 4309 hr in this same salt and loop. It should be noted that the niobium-modified specimens gained more weight than they lost. This is most probably due to mass transfer of iron from the standard Hastelloy N tubing, which contains about 5 wt % Fe, to the modified alloy, which has essentially no iron. Taking into account the value at which the corrosion rate of the modified Hastelloy N seems to be leveling out, we expect that the corrosion resistance of the 1%-Nb-modified Hastelloy N is at least as good as that of standard Hastelloy N.

Table 3. Corrosion Rate Measurement for Hastelloy N Specimens Exposed in FCL-2B

Alloy	Exposure	Corrosion Rate, $\text{mg cm}^{-2} \text{ year}^{-1}$, at Each Exposure Temperature		
		566°C	635°C	704°C
Standard	4309 hr	+0.02	-0.20	-2.31
1%-Nb-Modified	first 580 hr			-0.52
	next 497 hr			-0.31
	next 496 hr	+1.69	+2.31	-0.38
	next 669 hr	-0.46	+0.91	-0.28

CONCLUSIONS

The following conclusions can be drawn from this work.

1. Voltammetry provides a very convenient means for on-line measurement of the oxidation potential and impurity concentration of the salt.

2. Inconel 601 would probably not have sufficient corrosion resistance to be acceptable for use as a containment vessel material.

3. No evidence of the formation of uranium carbide was found in studies of the reaction of graphite with very reducing salt.

4. Weight loss of Hastelloy N specimens occurred as a linear function of the square root of the exposure time indicating diffusion-controlled corrosion.

5. Type 316 stainless steel has a high initial corrosion rate in as-received Li_2BeF_4 , but has a very low corrosion rate when beryllium is added to the salt.

6. Alloys of Hastelloy N modified by the addition of chromium showed weight losses proportional to the chromium concentration.

7. Limited results indicate that the corrosion rates of 1- and 3.4%-Nb-modified Hastelloy N are at least as good as that of standard Hastelloy N.

ACKNOWLEDGMENTS

The author wishes to gratefully acknowledge the following persons; for their contributions; E. J. Lawrence for operation of the thermal-convection loops, W. R. Huntley and H. E. Robertson for operation of the forced-circulation loop, H. E. McCoy, J. R. DiStefano, and J. H. DeVan for their advice and helpful discussions, and S. Peterson for editing and Gail Golliher for preparing the manuscript.

THIS PAGE
WAS INTENTIONALLY
LEFT BLANK

ORNL/TM-5783
 Distribution
 Category UC-76

INTERNAL DISTRIBUTION

- | | | | |
|--------|-------------------------------|-----|---------------------------------|
| 1-2. | Central Research Library | 51. | A. D. Kelmers |
| 3. | Document Reference Section | 52. | R. E. MacPherson |
| 4-13. | Laboratory Records Department | 53. | G. Mamantov |
| 14. | Laboratory Records, ORNL RC | 54. | D. L. Manning |
| 15. | ORNL Patent Office | 55. | C. L. Matthews |
| 16. | C. F. Baes | 56. | L. Maya |
| 17. | C. E. Bamberger | 57. | H. E. McCoy |
| 18. | E. S. Bettis | 58. | C. J. McHargue |
| 19. | C. R. Brinkman | 59. | L. E. McNeese |
| 20. | J. Brynestad | 60. | H. Postma |
| 21. | D. A. Canonico | 61. | T. K. Roche |
| 22. | S. Cantor | 62. | M. W. Rosenthal |
| 23. | C. B. Cavin | 63. | H. C. Savage |
| 24. | R. E. Clausing | 64. | J. E. Selle |
| 25. | J. L. Crowley | 65. | M. D. Silverman |
| 26. | F. L. Culler | 66. | G. M. Slaughter |
| 27. | J. E. Cunningham | 67. | A. N. Smith |
| 28. | J. H. DeVan | 68. | L. M. Toth |
| 29. | J. R. DiStefano | 69. | D. B. Trauger |
| 30. | R. G. Donnelly | 70. | J. R. Weir, Jr. |
| 31. | J. R. Engel | 71. | C. L. White |
| 32. | L. M. Ferris | 72. | J. P. Young |
| 33. | G. M. Goodwin | 73. | R. W. Balluffi (consultant) |
| 34. | W. R. Grimes | 74. | P. M. Brister (consultant) |
| 35. | R. H. Guymon | 75. | W. R. Hibbard, Jr. (consultant) |
| 36. | J. R. Hightower, Jr. | 76. | Hayne Palmour III (consultant) |
| 37-39. | M. R. Hill | 77. | N. E. Promisel (consultant) |
| 40. | W. R. Huntley | 78. | D. F. Stein (consultant) |
| 41-50. | J. R. Keiser | | |

EXTERNAL DISTRIBUTION

- 79-80. ERDA OAK RIDGE OPERATIONS OFFICE, P. O. Box E, Oak Ridge, TN 37830
 Director, Reactor Division
 Research and Technical Support Division
- 81-82. ERDA DIVISION OF NUCLEAR RESEARCH AND APPLICATION, Washington, DC 20545
 Director
- 83-196. ERDA TECHNICAL INFORMATION CENTER, Office of Information Services,
 P. O. Box 62, Oak Ridge, TN 37830
 For distribution as shown in TID-4500 Distribution Category,
 UC-76 (Molten Salt Reactor Technology):